

# Technical Datasheet


 Unit Display: English

[Print Now](#)
[E-Mail Datasheet](#)  
[Add to My Materials](#)

## D2 Tool Steel

### Identification

#### UNS Number

- T30402

#### AISI Number

- Type D2

### Type Analysis

<b>Carbon</b>	1.50 %	<b>Manganese</b>	0.50 %
<b>Silicon</b>	0.30 %	<b>Chromium</b>	12.00 %
<b>Molybdenum</b>	0.80 %	<b>Vanadium</b>	0.90 %
<b>Iron</b>	Balance		

### General Information

#### Description

D2 tool steel is an air hardening, high-carbon, high-chromium tool steel possessing extremely high wear resisting properties. It is very deep hardening and is practically free from size change after proper treatment. This tool steel's high chromium content gives it mild corrosion resisting properties in the hardened condition. D2 tool steel is available in the form of DeCarb-Free(DCF) bars. DCF bars have been cold finished in the mill prior to shipment, eliminating the need for bark removal by the tool and die fabricator.

#### Applications

D2 tool steel has found application in:

Blanking dies  
 Forming dies  
 Coining dies  
 Extrusion dies  
 Drawing dies  
 Forming rolls  
 Edging rolls  
 Beading rolls  
 Master tools  
 Heading tools  
 Long punches  
 Intricate punches  
 Slitting cutters

### Properties

#### Physical Properties

##### Specific Gravity

-- 7.83

##### Density

-- 0.2830 lb/in<sup>3</sup>

##### Mean Coefficient of Thermal Expansion

68°F, 212°F	$5.83 \times 10^{-6}$ in/in/°F
68°F, 392°F	$6.28 \times 10^{-6}$ in/in/°F
68°F, 572°F	$6.56 \times 10^{-6}$ in/in/°F
68°F, 752°F	$6.78 \times 10^{-6}$ in/in/°F
68°F, 932°F	$6.94 \times 10^{-6}$ in/in/°F
68°F, 1112°F	$7.00 \times 10^{-6}$ in/in/°F
68°F, 1292°F	$7.11 \times 10^{-6}$ in/in/°F
68°F, 1472°F	$7.22 \times 10^{-6}$ in/in/°F


#### Mean Coefficient of Thermal Expansion—D2 Tool Steel

The following figures are the average coefficients between room temperature and the specified elevated temperature. They represent material in the annealed condition and the dimensions are in in/in/° temperature.

Room Temperature		Average Coefficient	
68°F to	20°C to	10 <sup>4</sup> /°F	10 <sup>4</sup> /°C
212	100	5.81	10.5
392	200	6.29	11.3
572	300	6.56	11.8
752	400	6.76	12.2
932	500	6.93	12.5
1112	600	7.00	12.6
1292	700	7.09	12.8
1472	800	7.24	13.0

## Isothermal Transformation Diagram—D2 Tool Steel

Austenitizing Temperature - 1800° F (982° C)

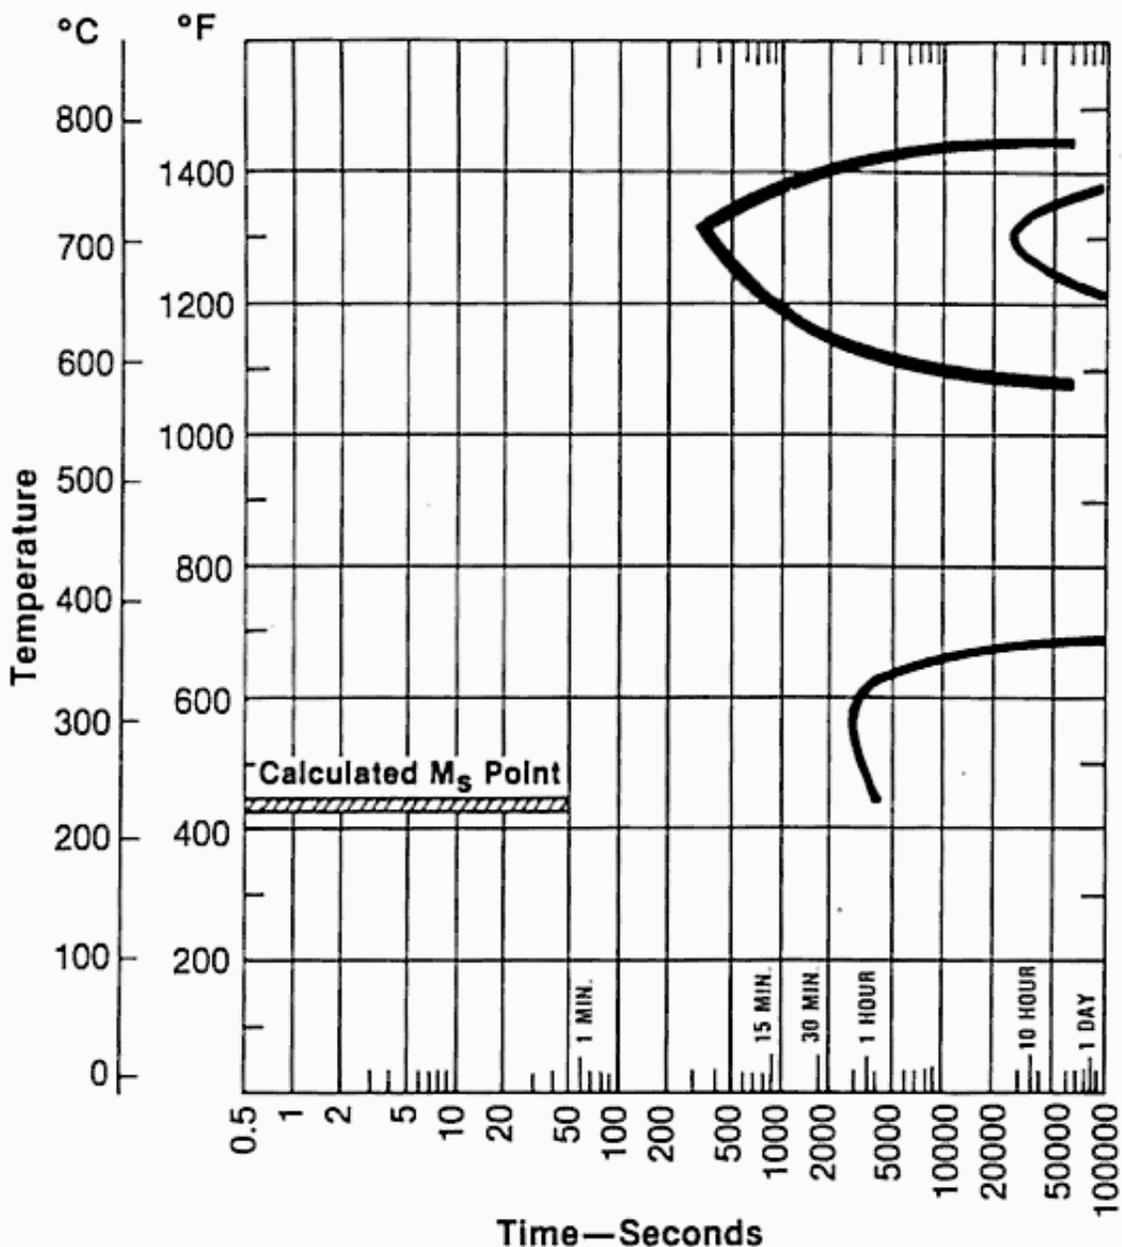

### Typical Mechanical Properties

High-carbon, high-chromium steels such as D2 tool steel achieve their excellent wear resistance due to a chemical balance which renders them notch sensitive and low in ductility. Meaningful tensile data are unavailable. The practical experience indicates that compressive loads in excess of 400,000 psi (2758 Mpa) can be withstood if evenly applied at low rates of loading.

### Heat Treatment

#### Decarburization

Like all high-carbon tool steels, D2 tool steel is subject to decarburization during thermal processing. Precautions must be taken to control this condition. Modern furnaces are available which proved

environments designed to minimize decarburization.

---

### **Normalizing**

---

Normalizing is not recommended for D2 tool steel and is not necessary after furnace cooling.

---

### **Annealing**

---

D2 tool steel should be packed in a suitable container, using a neutral packing compound, or placed in a controlled atmosphere furnace. Heat uniformly to 1550/1600°F (843/871°C), then cool very slowly in the furnace at a rate of not more than 20°F (11.1°C) per hour until the furnace is black. The furnace may then be turned off and allowed to cool naturally. This practice will produce a maximum hardness of Brinell 241.

---

### **Hardening**

---

D2 tool steel is extremely sensitive to overheating during hardening. It is therefore imperative that care be taken to insure that the hardening temperature is within the recommended range of 1800/1875°F (982/1024°C). If overheated, D2 tool steel, like other high-carbon, high-chrome tool steels, will not reach its maximum obtainable hardness and will shrink badly. Don't overheat it. Without preheating, place the tool right in the hot furnace and let it heat naturally until its color uniformly matches the color of the thermocouple in the furnace. Tools should be soaked at temperature 20 minutes plus 5 minutes for each inch of thickness, then quenched in air. Control of decarburization can be achieved by using any one of the several modern heat-treating furnaces designed for this purpose. If endothermic atmospheres are used a dew point between 20/40°F (-6.7/+4.4°C) is suggested. In older type, manually operated exothermic atmosphere furnaces, an oxidizing atmosphere is required. Excess oxygen of about 4 to 6% is preferred. If no atmosphere is available, the tool should be pack hardened or wrapped in stainless steel to protect its surface.

---


### **Deformation (Size Change) in Hardening**

---

The accompanying chart within the hyperlink entitled "Size Change" shows typical length changes of D2 tool steel when it has been properly hardened and tempered. Note that the length change information is presented in inches per inch of original length. The chart indicates that this material can be expected to expand when tempered to temperatures below 625°F (329°C). When tempered between 625°F (329°C) and 950°F (510°C) it will shrink. Tool steels hold size best when quenched from the proper hardening temperature. If overheated, they tend to show severe shrinkage after tempering.

## Size Change—D2 Tool Steel

1" (25.4 mm) round, air quenched from 1850° F (1010° C), tempered 1 hour at indicated temperature.

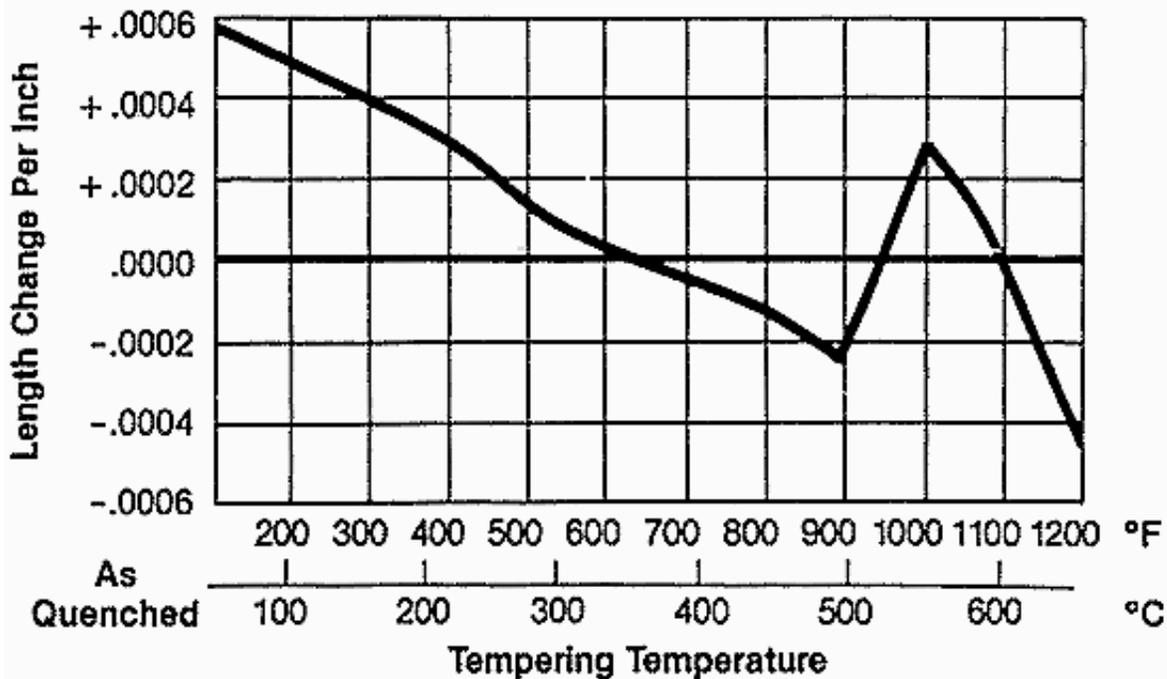

### Stress Relieving

To relieve machining stresses for greater accuracy in hardening, first rough machine, then heat to temperature of 1200/1250°F (649/677°C) and slowly cool. After cooling, the part or parts may be finish machined.

### Tempering

D2 tool steel has two toughness peaks, one at 450°F (232°C) and the other at 700°F (371°C). For the best combination of toughness and hardness, temper at 450°F (232°C). While this is the best tempering temperature for practically all applications, greater ductility can be obtained by tempering at 700°F (371°C), although there will be some sacrifice of hardness. Double tempering is desired with the second temper 25°F (13.8°C) below the first temper. The hardness curve for D2 tool steel shows the same "kickback" or secondary hardening found in high-speed steels. In this material, it occurs at 1000°F (538°C) and, if by accident tools have been overheated in hardening, causing shrinkage and loss of hardness, they might be salvaged by tempering them at 1000°F (538°C). They will regain some of their lost hardness and will expand close to their former size. The hardness values given in the chart at 1000°F (538°C) are based on 1 hour soaking time. Longer soaking time will result in somewhat lower Rockwell C hardness. Since D2 tool steel maintains a high hardness after a 1000°F (538°C) temper, it lends itself well to gas nitriding or liquid cyaniding. This provides added wear resistance for forming tools.

**Effect of Tempering Temperature on Hardness—D2 Tool Steel**

Air quenched from 1850° F (1010° C), tempered 1 hour at indicated temperature

Tempering Temperature		Rockwell C Hardness	Equivalent Scleroscope
°F	°C		
As Hardened		62/63	88
200	93	61/62	86
400	204	59/60	83
450	232	59/60	83
550	288	56/57	77
700	371	56/57	77
800	427	56/57	77
900	482	58/59	82
1000	538	59/60	83
1100	593	50/55	70
1200	649	44/45	58

**Workability****Forging**

D2 tool steel forges very much like high-speed steel. Heat uniformly and forge from a temperature of 1925/2000°F (1052/1093°C). Do not continue to forge below 1700°F (927°C). Reheat as often as necessary to maintain proper forging temperature. Small, simple forgings can be cooled slowly in lime. The best practice for large forgings is to place them in a furnace heated to approximately 1550°F (843°C), soak uniformly at this temperature, then shut off the heat and allow the material to cool slowly in the furnace. This is not an anneal. After the forging is cold, it must be annealed as discussed in the section of this datasheet entitled "Annealing."

**Machinability**

The machinability of D2 tool steel may be rated between 35 and 40% of Type W-1 tool steel, or about 25 to 30% of B1112.

Following are typical feeds and speeds for D2 tool steel.

**Turning—Single Point and Box Tools**

Depth of Cut In.	High-Speed Tools			Carbide			
	Speed, fpm	Feed, lpr	Tool Material	Speed, fpm		Feed, lpr	Tool Material
				Brazed	Throw Away		
.150	45	.010	M-2	160	210	.010	C-6
.025	60	.005	M-3	210	250	.005	C-7

**Turning—Cut-Off and Form Tools**

Speed, fpm	Feed, lpr							Tool Material
	Cut-Off Tool Width, Inches			Form Tool Width, Inches				
	1/16	1/8	1/4	1/2	1	1-1/2	2	
45	.001	.001	.0015	.0015	.001	.0007	.0007	M-2
145	.002	.002	.003	.0025	.0015	.0015	.0015	C-6

**Drilling**

Speed, fpm	Feed, ipr								Tool Material
	Nominal Hole Diameter, Inches								
	1/16	1/8	1/4	1/2	3/4	1	1-1/2	2	
30	.001	.001	.003	.005	.007	.008	.010	.012	M-42

## Reaming

Speed, fpm	High-Speed Tool						Carbide Tool		
	Feed, ipr						Tool Material	Speed, fpm	Tool Material
	Reamer Diameter, Inches								
1/8	1/4	1/2	1	1-1/2	2				
25	.002	.003	.005	.007	.010	.012	M-7	80	C-2

## Milling—End Peripheral

Depth of Cut In.	High-Speed Tools						Carbide Tools					
	Speed, fpm	Feed—Inches per tooth				Tool Material	Speed, fpm	Feed—Inches per tooth				Tool Material
		Cutter Diameter, Inches						Cutter Diameter, Inches				
		1/4	1/2	3/4	1-2			1/4	1/2	3/4	1-2	
.050	55	.001	.002	.003	.004	M-2;M-7	200	.0015	.0025	.004	.005	C-6

## Broaching

Speed, fpm	Chip Load, Inches per tooth	Tool Material
10	.002	M-42

## Sawing—Power Hack Saw

Pitch—Teeth per Inch				Speed	Feed
Material Thickness, Inches					
Under 1/4	1/4-3/4	3/4-2	Over 2	Strokes/Minute	Inches/Stroke
10	6	6	4	140	.006
10	6	6	4	70	.003
10	10	6	4	85	.003
10	10	6	4	55	.005
10	8	6	4	75	.003

Figures used for all metal removal operations covered are average. On certain work, the nature of the part may require adjustment of speeds and feeds. Each job has to be developed for best production results with optimum tool life. Speeds and feeds should be increased or decreased in small steps.

---

**Additional Machinability Notes**


---

Figures used for all metal removal operations covered are average. On certain work, the nature of the part may require adjustment of speeds and feeds. Each job has to be developed for best production results with optimum tool life. Speeds and feeds should be increased or decreased in small steps.

---

**Other Information**


---

**Wear Resistance**

All specimens air hardened from 1850°F (1010°C) and tempered 1 hour at indicated temperature. The wear characteristics shown in the chart were generated using ASTM G65 Procedure A, which is the ASTM Standard Practice for Conducting Dry Sand/Rubber Wheel Abrasions Tests. The data are

presented as a volume loss as required by the ASTM standard. Note that a lower number indicates better wear resistance.

### Dry Sand/Rubber Wheel Abrasion Test—D2 Tool Steel

All specimens air hardened from 1850° F (1010° C) and tempered 1 hour at indicated temperature

Tempering Temperature		Rockwell C Hardness	Average Volume Loss ASTM
°F	°C		
As-Hardened		63/64	37.6
450	232	59.5	40.8
1075	579	52	53.0
1125	607	48	61.9
1200	649	43/44	85.9

The wear characteristics shown in the chart were generated using ASTM G65 Procedure A, which is the ASTM Standard Practice for Conducting Dry Sand/Rubber Wheel Abrasion Tests.

The data are presented as a volume loss as required by the ASTM standard. Note that a lower number indicates better wear resistance.

#### Applicable Specifications

- ASTM A681
- QQ-T-570

#### Forms Manufactured

- Bar-Rounds
- Billet
- Wire

#### Technical Articles

- A Three-Point Program for Improving the Performance of Cold Work Tooling
- Coated Tools of High Strength, High Tough Steel Produce up to 100 Times More Powder Metal Parts
- Forging Difficult Alloys: How to Get Better Results, Consistently
- New Powder Metal Die Steel for Cold Work Tooling Applications

#### Disclaimer:

The information and data presented herein are typical or average values and are not a guarantee of maximum or minimum values. Applications specifically suggested for material described herein are made solely for the purpose of illustration to enable the reader to make his/her own evaluation and are not intended as warranties, either express or implied, of fitness for these or other purposes. There is no representation that the recipient of this literature will receive updated editions as they become available.

Unless otherwise specified, registered trademarks are property of CRS Holdings Inc., a subsidiary of [Carpenter Technology Corporation](#).  
Copyright 2009 CRS Holdings Inc. All rights reserved.

Edition Date: 07/01/2000